

APPROVALS 批准					DOCUMENT TITLE 文件	
DEPT 部门	NAME 名字	TITLE 职位	SIGNATURE 签名	DATE 日期	Outgoing inspection report 出货检验报告	
QA	PeterLange	Quality vp	Lange	2024/3/28		
					Template Number	Corp-F-QA-30

Test Report

QR/QM-12


A/0

Grade	N35	Size	2x1mm	Date	2024/3/28	
Total Q'ty	50000	Samples	20PCS	Coating	NiCuNi	
Items	① 2	② 1	③	④	GAUSS	
Standard	±0.05	±0.05			N	S
Unit	mm	mm			Gs	
1	1.99	1.00			1930	2030
2	1.99	1.00			1930	2050
3	2.00	0.98			1930	2000
4	1.99	0.98			1880	2080
5	1.99	0.99			1960	2030
6	1.99	0.98			1910	2050
7	2.00	0.99			1930	2050
8	1.99	1.00			1880	2000
9	1.99	1.00			1960	2080
10	1.97	0.99			1910	2030
11	1.97	1.00			1930	2030
12	1.98	0.99			1930	2050
13	1.99	1.00			1880	2050
14	1.99	0.99			1960	2000
15	1.98	1.00			1910	2080
16	1.97	1.00			1930	2030
17	1.97	1.00			1930	2050
18	1.98	0.98			1930	2050
19	1.99	1.00			1880	2050
20	2.00	0.98			1960	2000
Max	2.00	1.00			1960	2080
Min	1.97	0.98			1880	2000
Avg	1.99	0.99			1923	2040
Decision	ok	ok			ok	ok

Inspector: Chengyongsheng

Verifier: Luronghai

Date: 2024/03/28

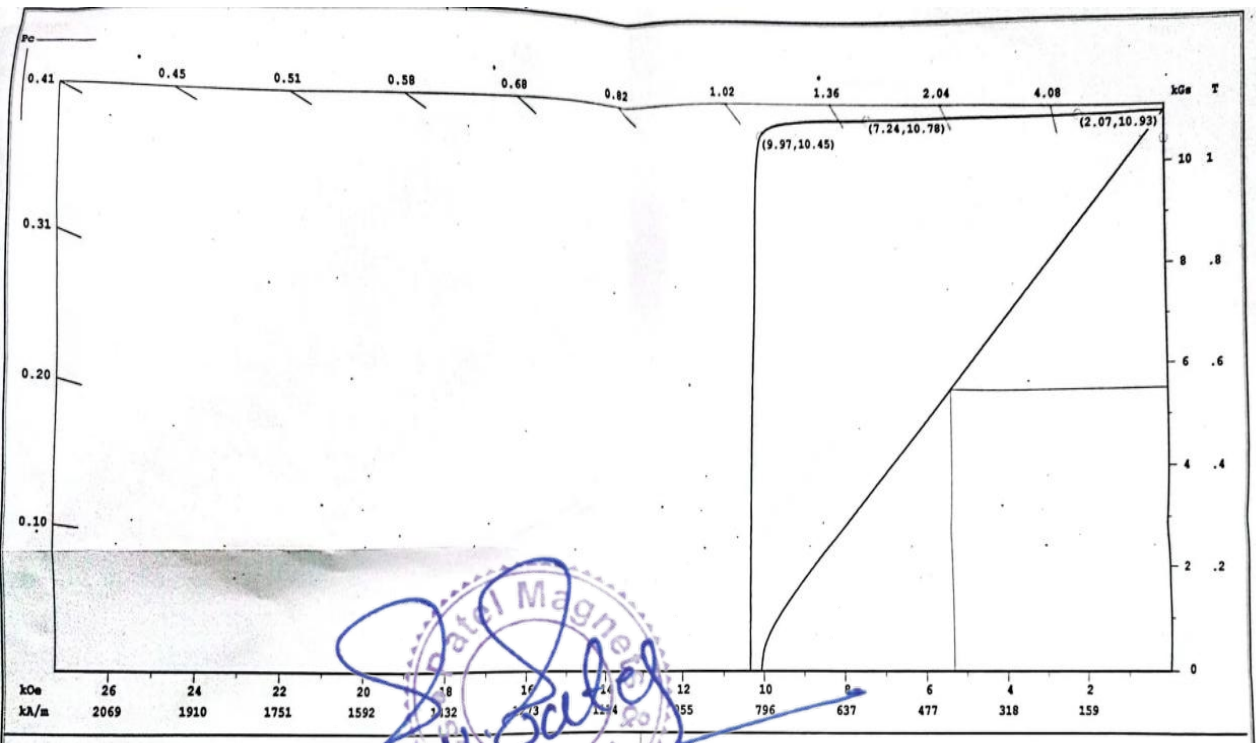

Br	=	1.099	T	10.99	kGs
Hcb	=	801	kA/m	10.06	kOe
Hcj	=	958	kA/m	12.34	kOe
(BH)max	=	233.32	kJ/m^3	29.32	MGOe
Hk	=	803	kA/m	10.09	kOe
Hd	=	424	kA/m	5.32	kOe
Bd	=	0.551	T	5.51	kGs
Hd5	=	793	kA/m	9.97	kOe
Hk/Hcj	=	97.5%			
(BH)max-Pc	=	1.04			

Material Type	:	NdFe	:
Patch No	:	5-1202-6	:
Sample No	:	N30	:
Test Date	:	2023-12-05	:
Sample Shape	:	Column	:
Size(mm)	:	24.96	:
Document No	:	23044839	:
SampleT(°C)	:	20	:
prec	:	1.092	:

AUTOMATIC HYSTERSIGRAPH MODE AMT-4A SJ LTD.