

APPROVALS 批准					DOCUMENT TITLE 文件	
DEPT 部门	NAME 名字	TITLE 职位	SIGNATURE 签名	DATE 日期	<b>Outgoing inspection report</b> <b>出货检验报告</b>	
QA	PeterLange	Quality vp	Lange	2024/4/3		
					Template Number	<b>Corp-F-QA-30</b>

## Test Report

QR/QM-12


A/0

Grade	N35	Size	3x1.5mm	Date	2024/4/3
Total Q'ty	10000	Samples	20PCS	Coating	NiCuNi
Items	①	②	③	④	GAUSS
	3	1.5			
Standard	+/-0.05	+/-0.05			N S
Unit	mm	mm			Gs
1	2.96	1.46			2560 2660
2	2.98	1.47			2540 2690
3	2.99	1.47			2650 2590
4	3.02	1.46			2790 2750
5	2.98	1.47			2610 2540
6	2.99	1.47			2530 2810
7	2.98	1.47			2650 2810
8	2.98	1.46			2680 2590
9	2.99	1.48			2790 2640
10	2.98	1.47			2670 2660
11	2.98	1.46			2620 2540
12	3.00	1.47			2610 2570
13	2.98	1.48			2660 2540
14	2.99	1.46			2690 2680
15	2.98	1.47			2670 2580
16	3.02	1.48			2650 2640
17	2.99	1.46			2580 2570
18	3.01	1.48			2670 2640
19	2.98	1.47			2620 2590
20	2.98	1.48			2580 2640
Max	3.02	1.48			2790 2810
Min	2.96	1.46			2530 2540
Avg	2.99	1.47			2641 2637
Decision	ok	ok			ok ok

Inspector: Chengyongsheng

Verifier: Yujiaming

Date 2024/04/3

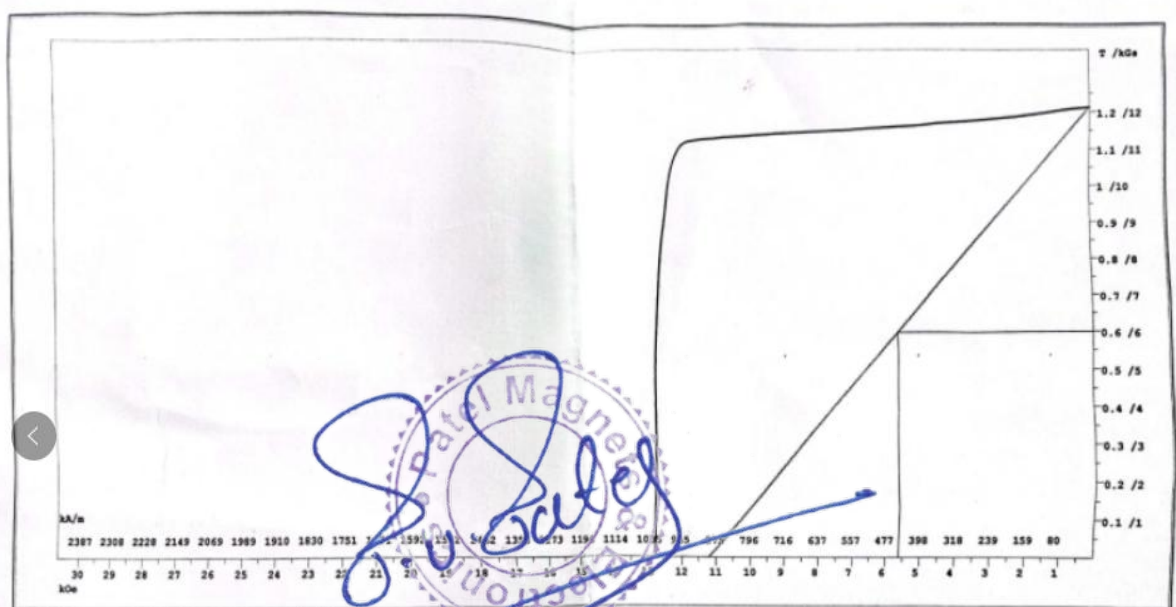

Br	= 1.212	T	12.12	kGs
Hcb	= 891	kA/m	11.20	kOe
Hcj	= 1016	kA/m	12.77	kOe
(BH)max	= 266.90	kJ/m <sup>3</sup>	33.54	MGoe
Hk	= 953	kA/m	11.97	kOe
Hd	= 446	kA/m	5.60	kOe
Bd	= 0.599	T	5.99	kGs
Hk/Hcj	= 93.8%			

Material Type:	
Patch No:	12-29
Sample No:	
Test Date:	2024-1-1
Sample Shape:	Column
Size (mm):	23.26
Document No:	240114
Sample T (°C):	20