

APPROVALS 批准					DOCUMENT TITLE 文件	
DEPT 部门	NAME 名字	TITLE 职位	SIGNATURE 签名	DATE 日期	Outgoing inspection report 出货检验报告	
QA	PeterLange	Quality vp	Lange	2024/1/17		
					Template Number 模板	Corp-F-QA-30

Test Report

QR/QM-12


A/0

Grade	N35	Size	L40*20*5	Date	2024/1/17	
Total Q'ty	800	Samples	20PCS	Coating	NiCuNi	
Items	①	②	③	④	GAUSS	
	40	20	5			
Standard	±0.05	±0.05	±0.05		N	S
Unit	mm	mm	mm		Gs	
1	39.98	19.99	5.01		3060	3190
2	39.91	20.00	4.98		3060	3210
3	39.92	20.00	4.99		3070	3220
4	39.99	20.00	4.98		3130	3100
5	40.03	20.00	4.98		3250	3250
6	40.00	19.99	4.98		3100	3090
7	40.01	20.00	4.98		3150	3080
8	40.00	20.00	4.99		3100	3060
9	40.00	19.99	5.00		3070	3070
10	40.00	19.98	4.98		3120	3130
11	40.01	19.99	4.98		3120	3190
12	39.99	20.00	4.99		3060	3100
13	39.98	19.98	4.99		3150	3150
14	40.01	20.00	4.97		3210	3100
15	40.01	19.99	4.98		3190	3250
16	39.98	20.00	4.97		3180	3100
17	39.99	19.98	4.98		3260	3180
18	40.01	19.97	4.99		3220	3260
19	40.01	19.98	4.97		3060	3130
20	39.99	19.99	4.98		3150	3250
Max	40.03	20.00	5.01		3260	3260
Min	39.91	19.97	4.97		3060	3060
Avg	39.99	19.99	4.98		3160	3160
Decision	ok	ok	ok		ok	ok

Inspector: Chengyongsheng

Verifier: Yujiaming

ate : 2024/01/1

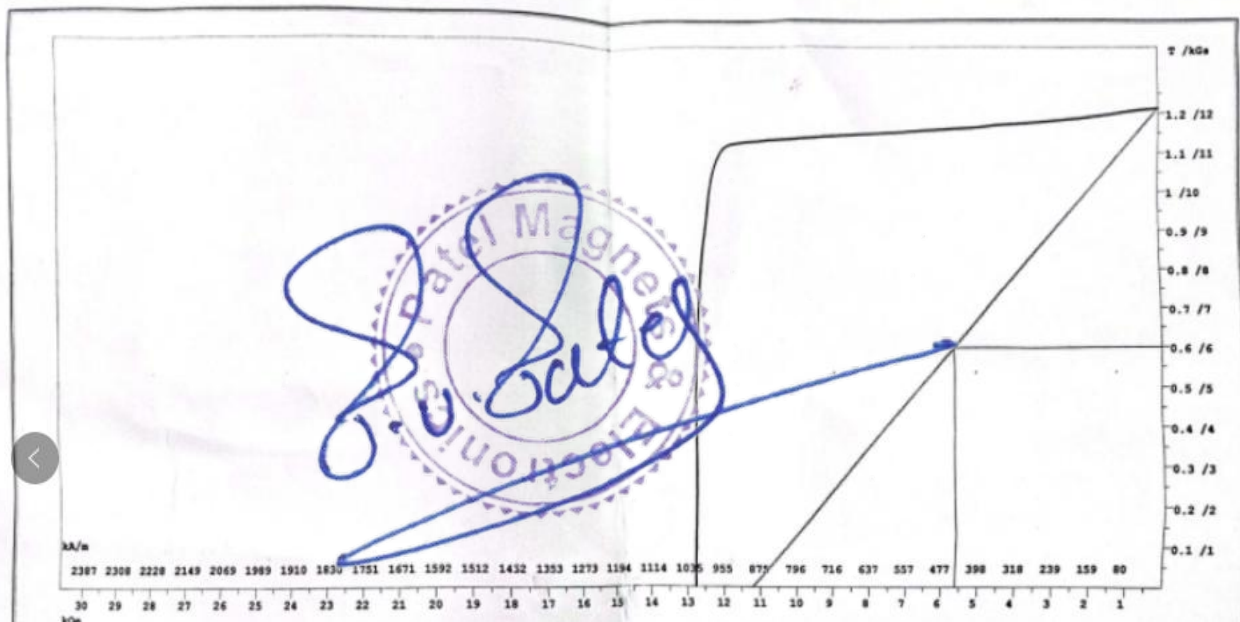

Br	= 1.212	T	12.12	kGs
Hcb	= 891	kA/m	11.20	kOe
Hcj	= 1016	kA/m	12.77	kOe
(BH)max	= 266.90	kJ/m ³	33.54	MGOe
Hk	= 953	kA/m	11.97	kOe
Hd	= 446	kA/m	5.60	kOe
Bd	= 0.599	T	5.99	kGs
Hk/Hcj	= 93.8%			

Material Type:	
Patch No:	12-29
Sample No:	
Test Date:	2024-1-1
Sample Shape:	Column
Size(mm):	23.26
Document No:	240114
SampleT(°C):	20